



In situ TEM electrical characterisation and patterning of graphene

Thomsen, Joachim Dahl; Gade, Carsten; Bøggild, Peter; Booth, Tim

Publication date:
2015

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Thomsen, J. D., Gade, C., Bøggild, P., & Booth, T. (2015). *In situ TEM electrical characterisation and patterning of graphene*. Poster session presented at Physics Boat Workshop 2015, Helsinki, Finland.

General rights


Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.


Introduction

- Transmission electron microscopy is an excellent characterisation tool, able to obtain information about the graphene structure on an atomic scale
- It can also be used to pattern the graphene through (1) knock-on damage from the beam, (2) etching with oxygen (in an environmental TEM), (3) nanoparticle etching
- Here we present our preliminary work with graphene in-situ TEM

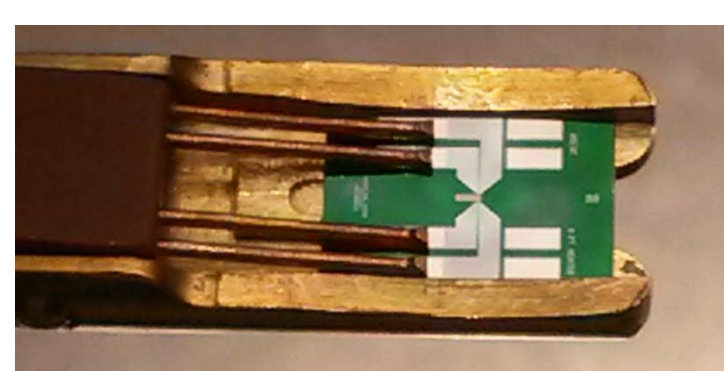


TEM Platforms


We have fabricated a variety of chips that are able to measure electrical properties and heat up.

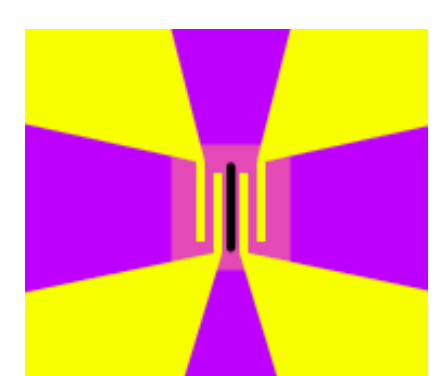


Schematic of the 4 point contact chip. Colour code: yellow – metal, purple – nitride surface, pink – freestanding nitride, black – opening in nitride (35 μm long)

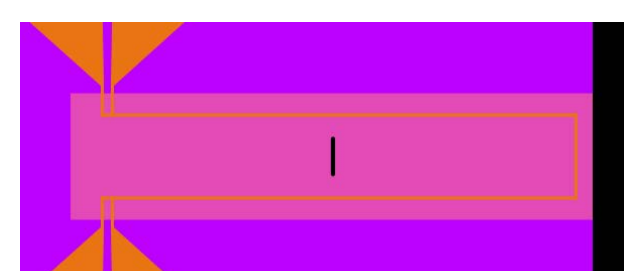

Schematic of the 4 point heater chip. Colour code: brown – encapsulated metal

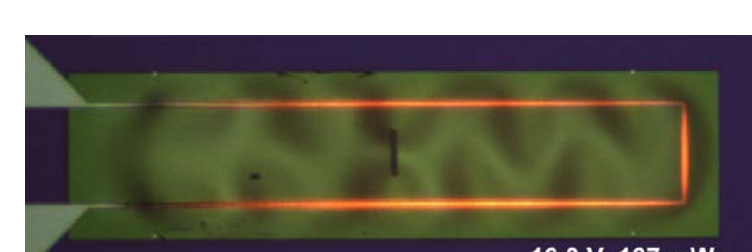


Chip glowing hot in normal atmosphere

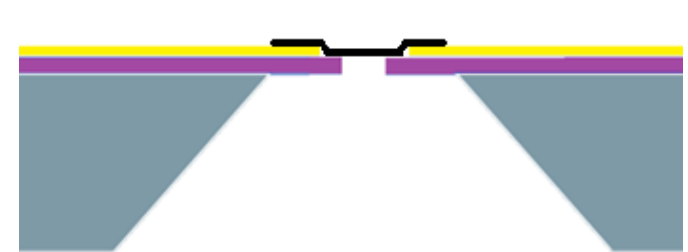


Cross sectional view – graphene on top

Graphene Transfer


We transfer graphene using the "wedging" method with cellulose acetate butyrate (CAB). We have reproducibly obtained graphene suspended over 15 μm trenches on our TEM platforms.

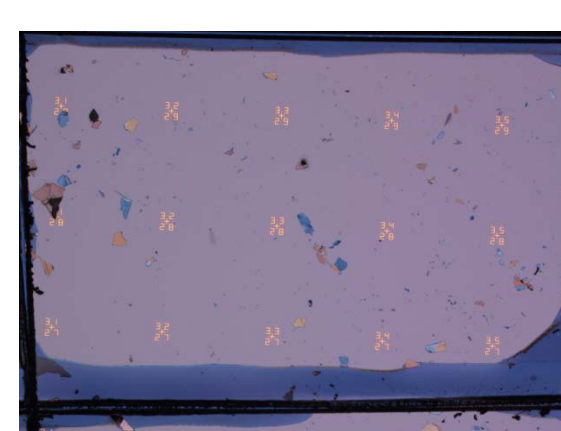


CAB cut

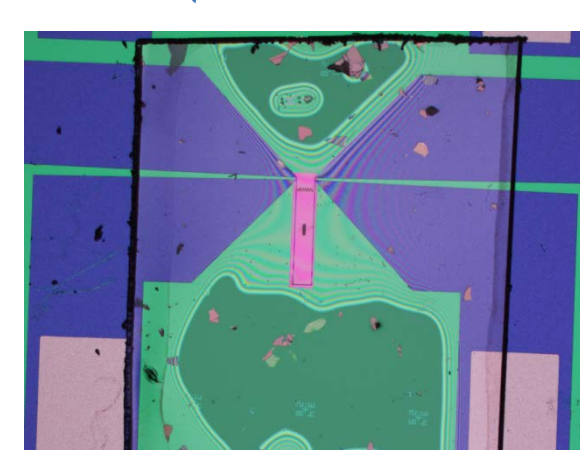


Transfer CAB to TEM chip

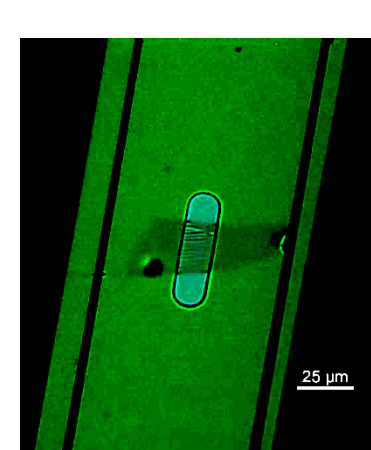

Bake to at least 135 $^{\circ}\text{C}$

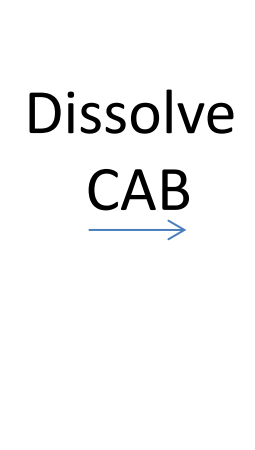







Dissolve CAB

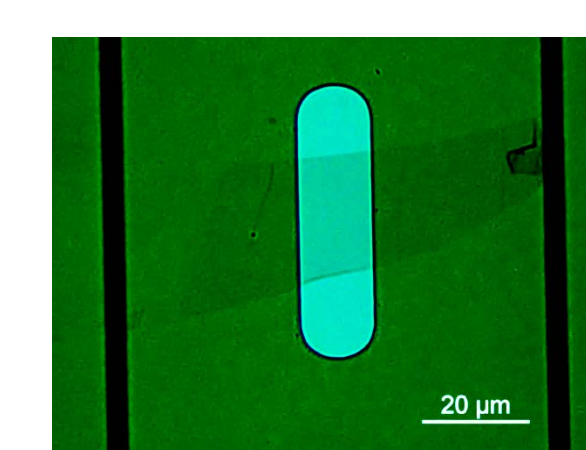

Critical point drying

Twisted Bilayers



We have fabricated samples of stacked incommensurate monolayers ("twisted bilayers") using wedging transfer to place a graphene flake on top of another. The stack is then transferred to the TEM platform.

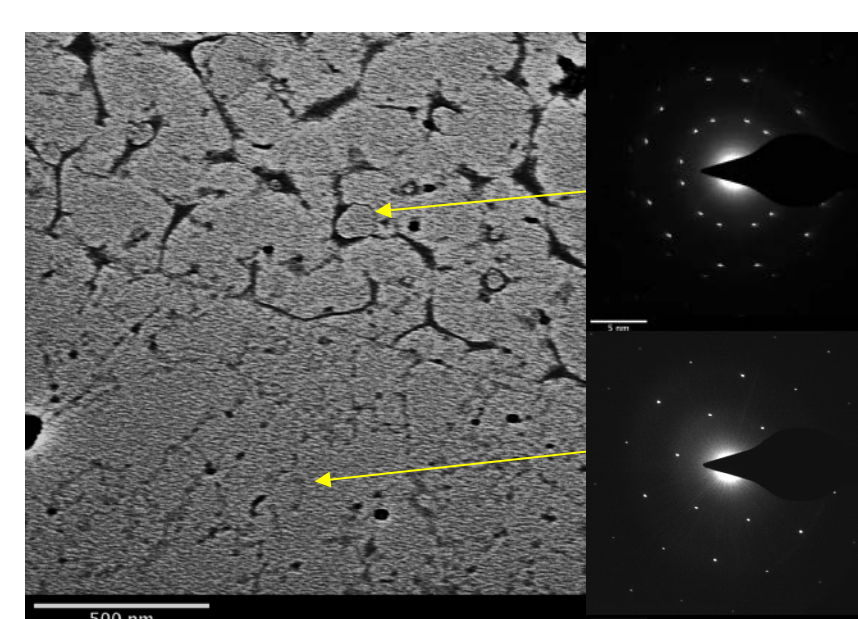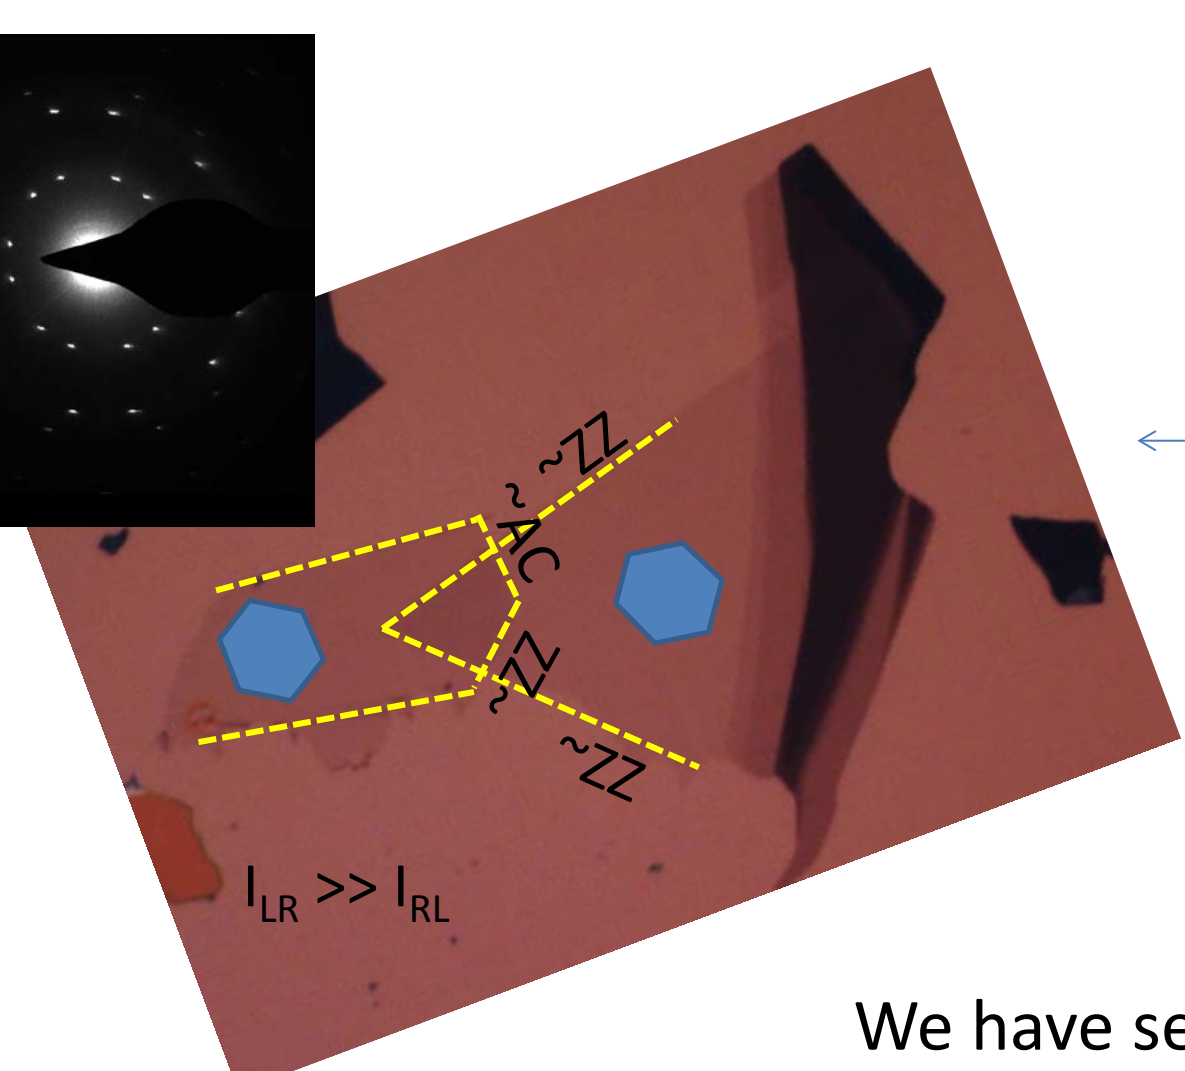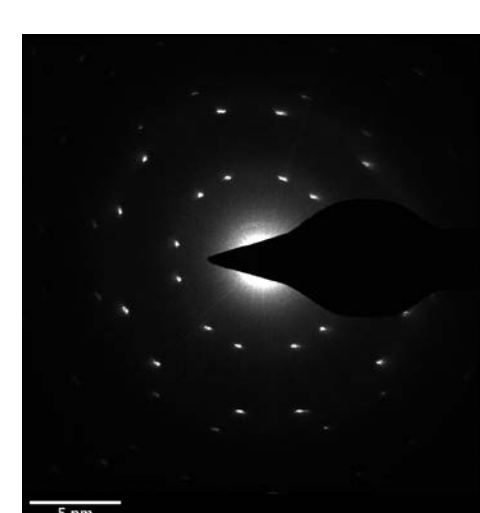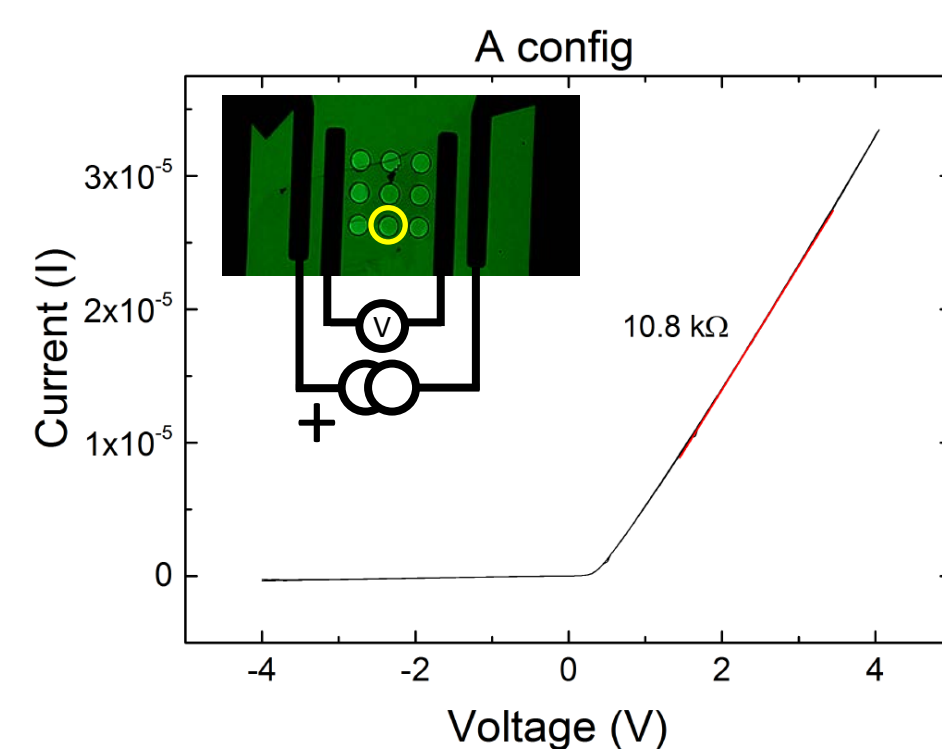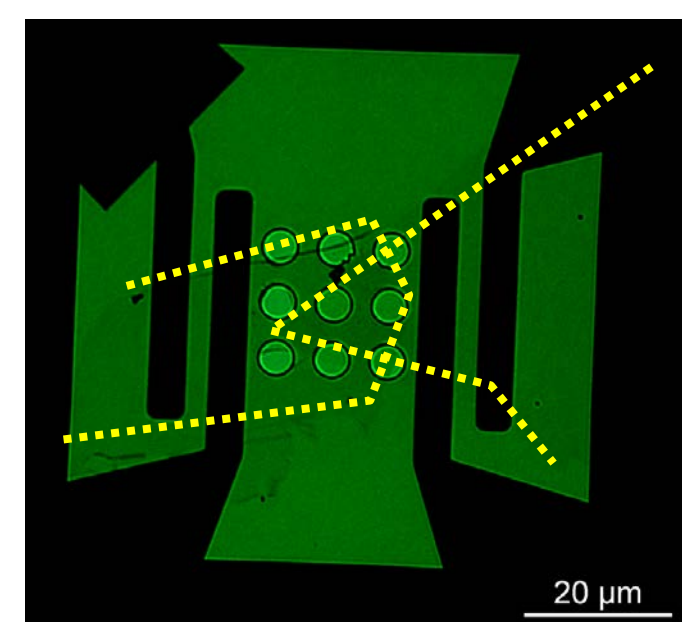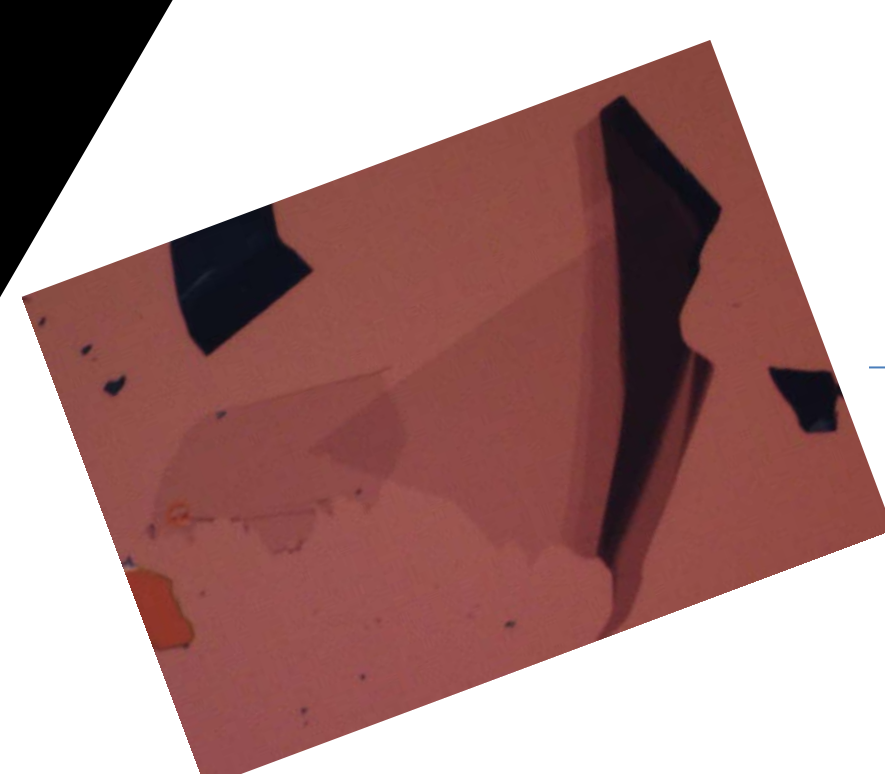


We have seen a diode-like behavior in this sample with straight edges

Graphene Constriction


- Using knock-on damage we can structure the graphene by focusing the beam to a small area as possible, in this case forming a constriction.

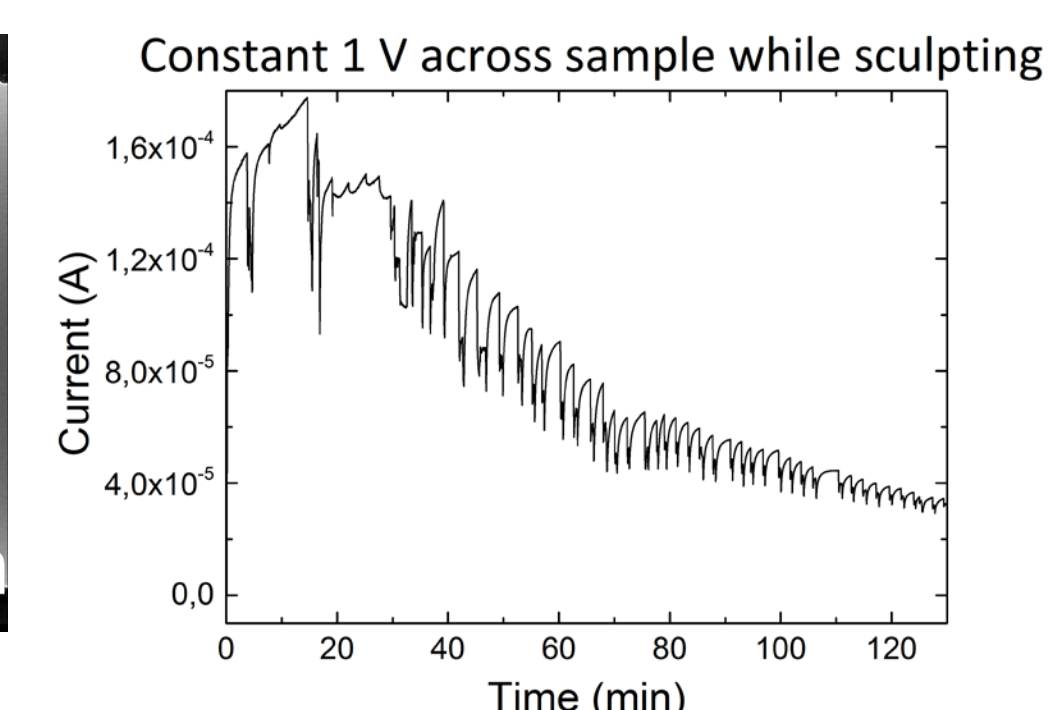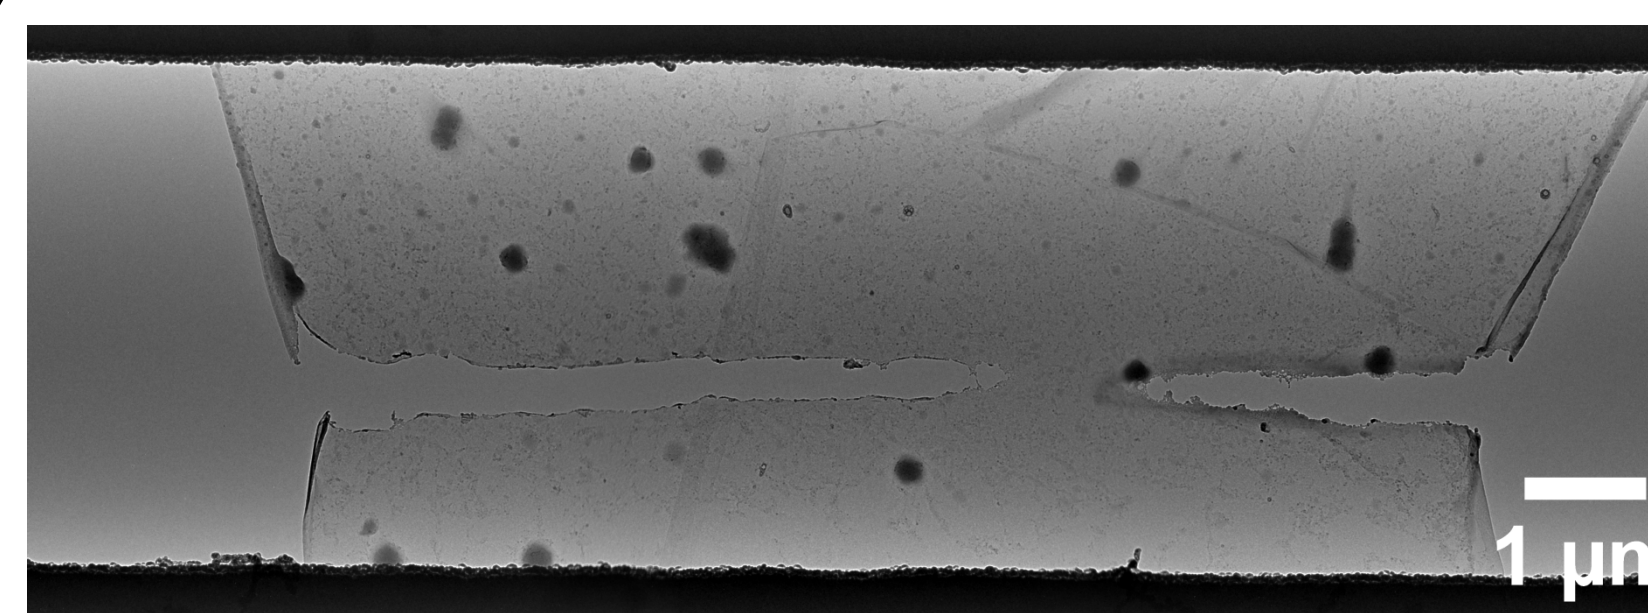

- After sculpting we swept the voltage until the constriction broke


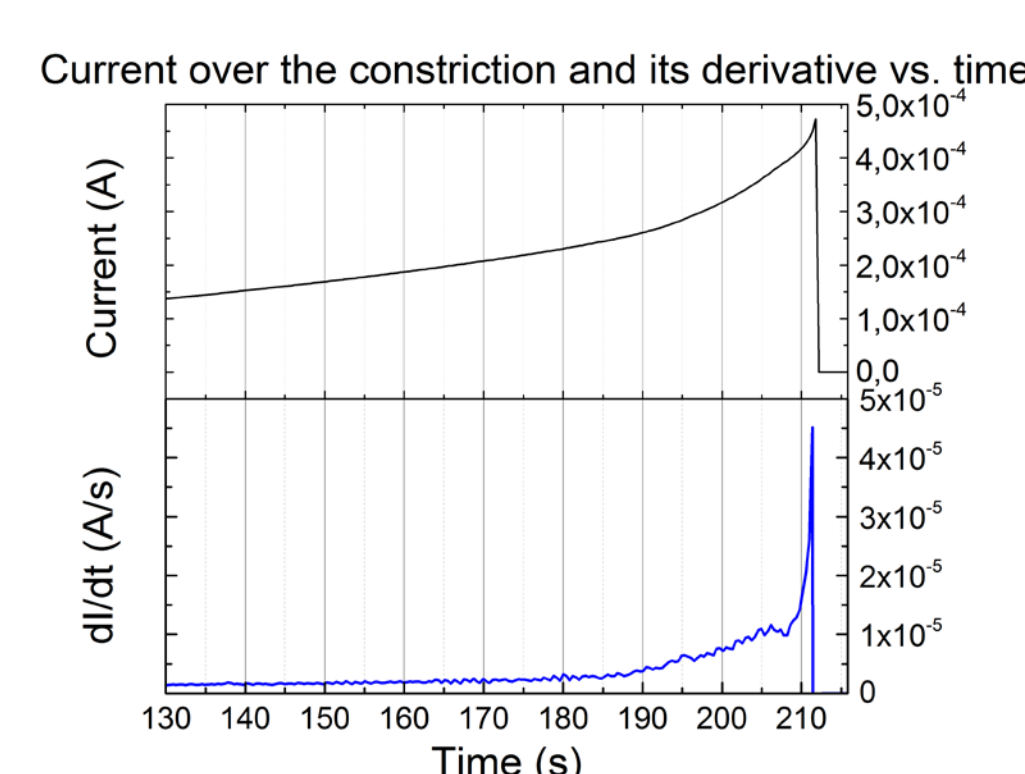


- High resolution images of the broken area shows indications of heating

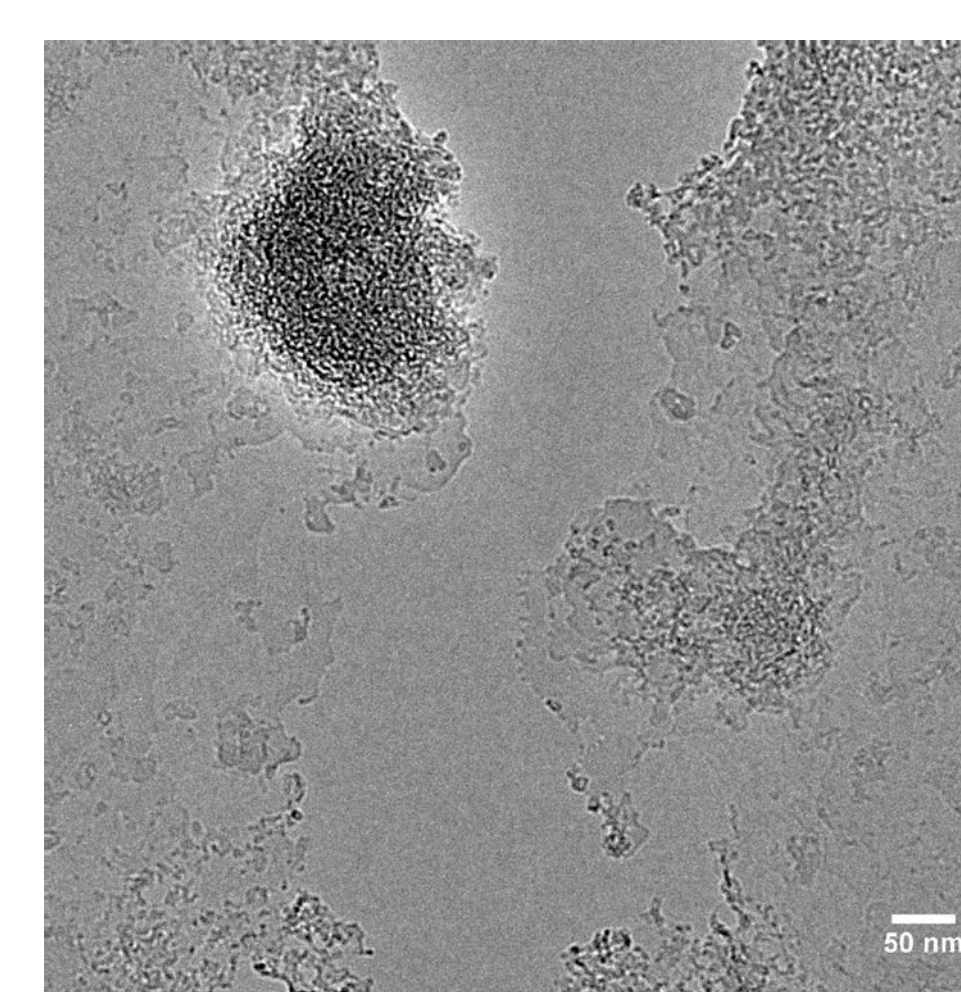


Cleaning Graphene

Current annealing in normal atmosphere

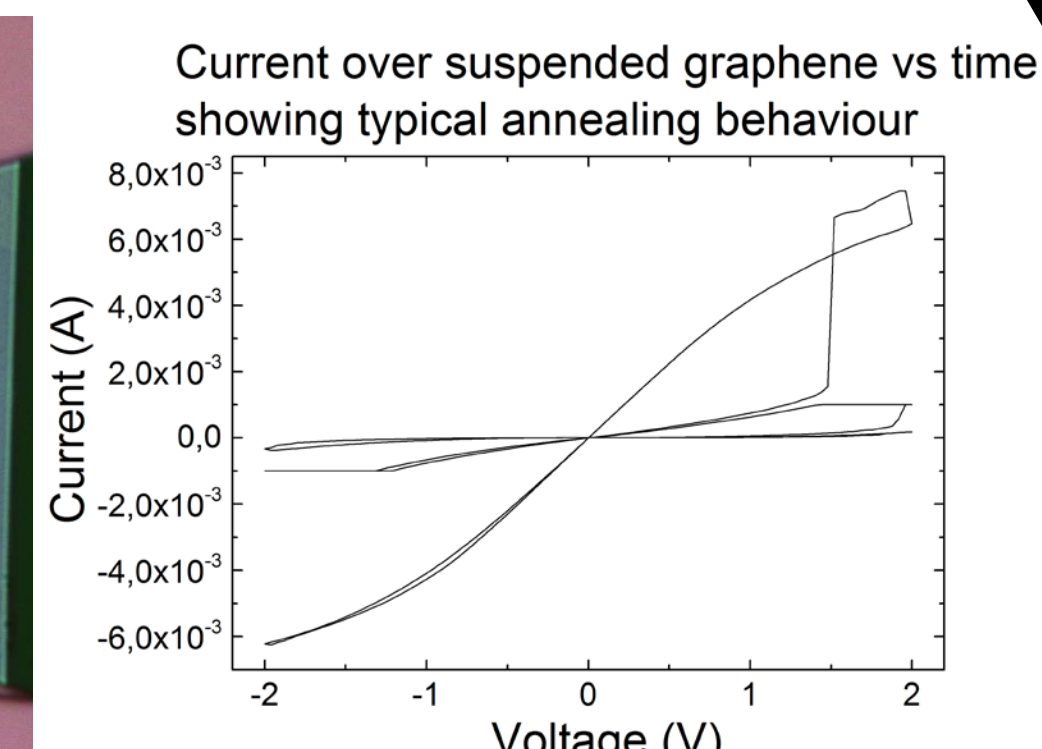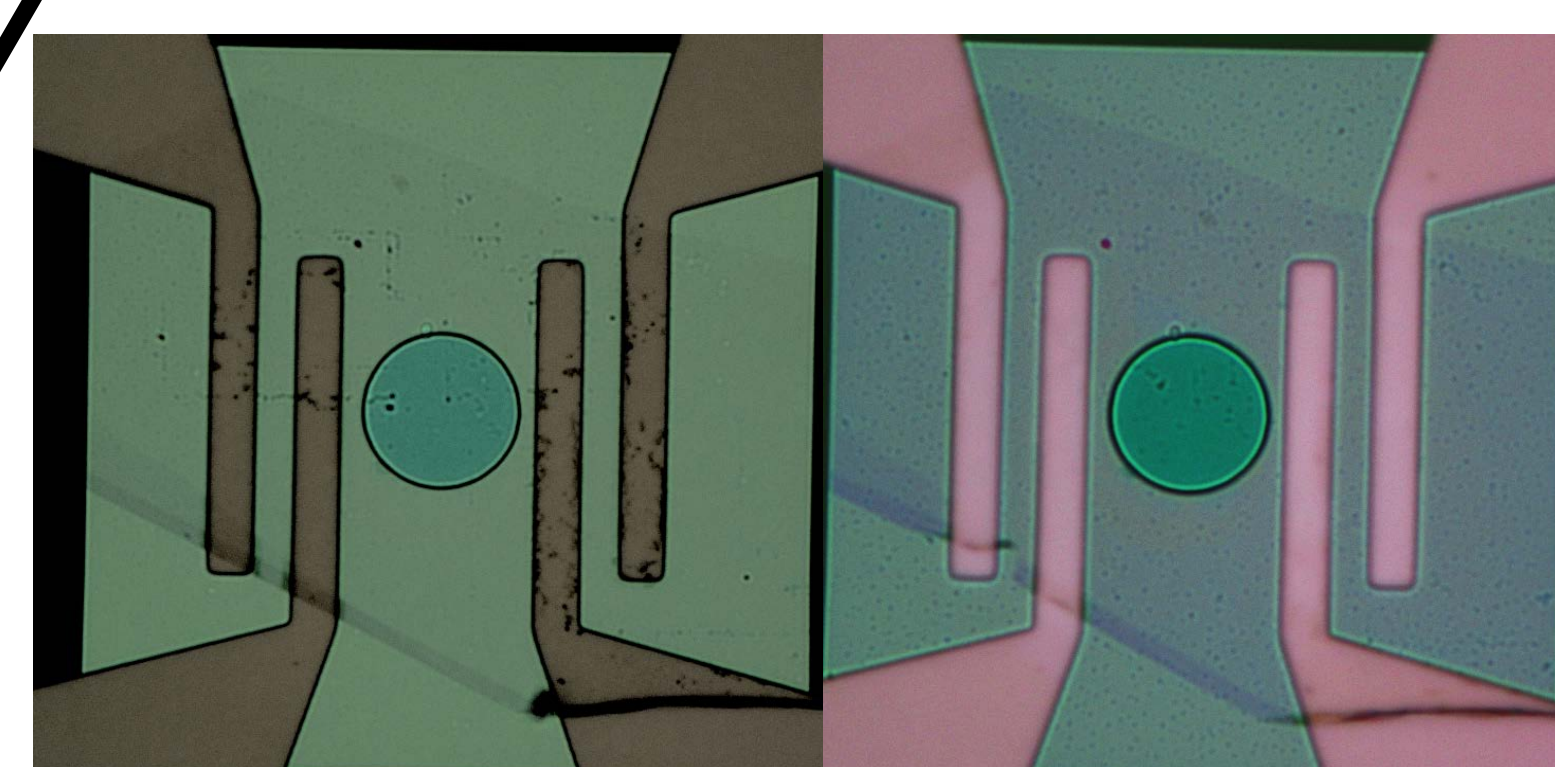

In-situ TEM by the on-chip heater

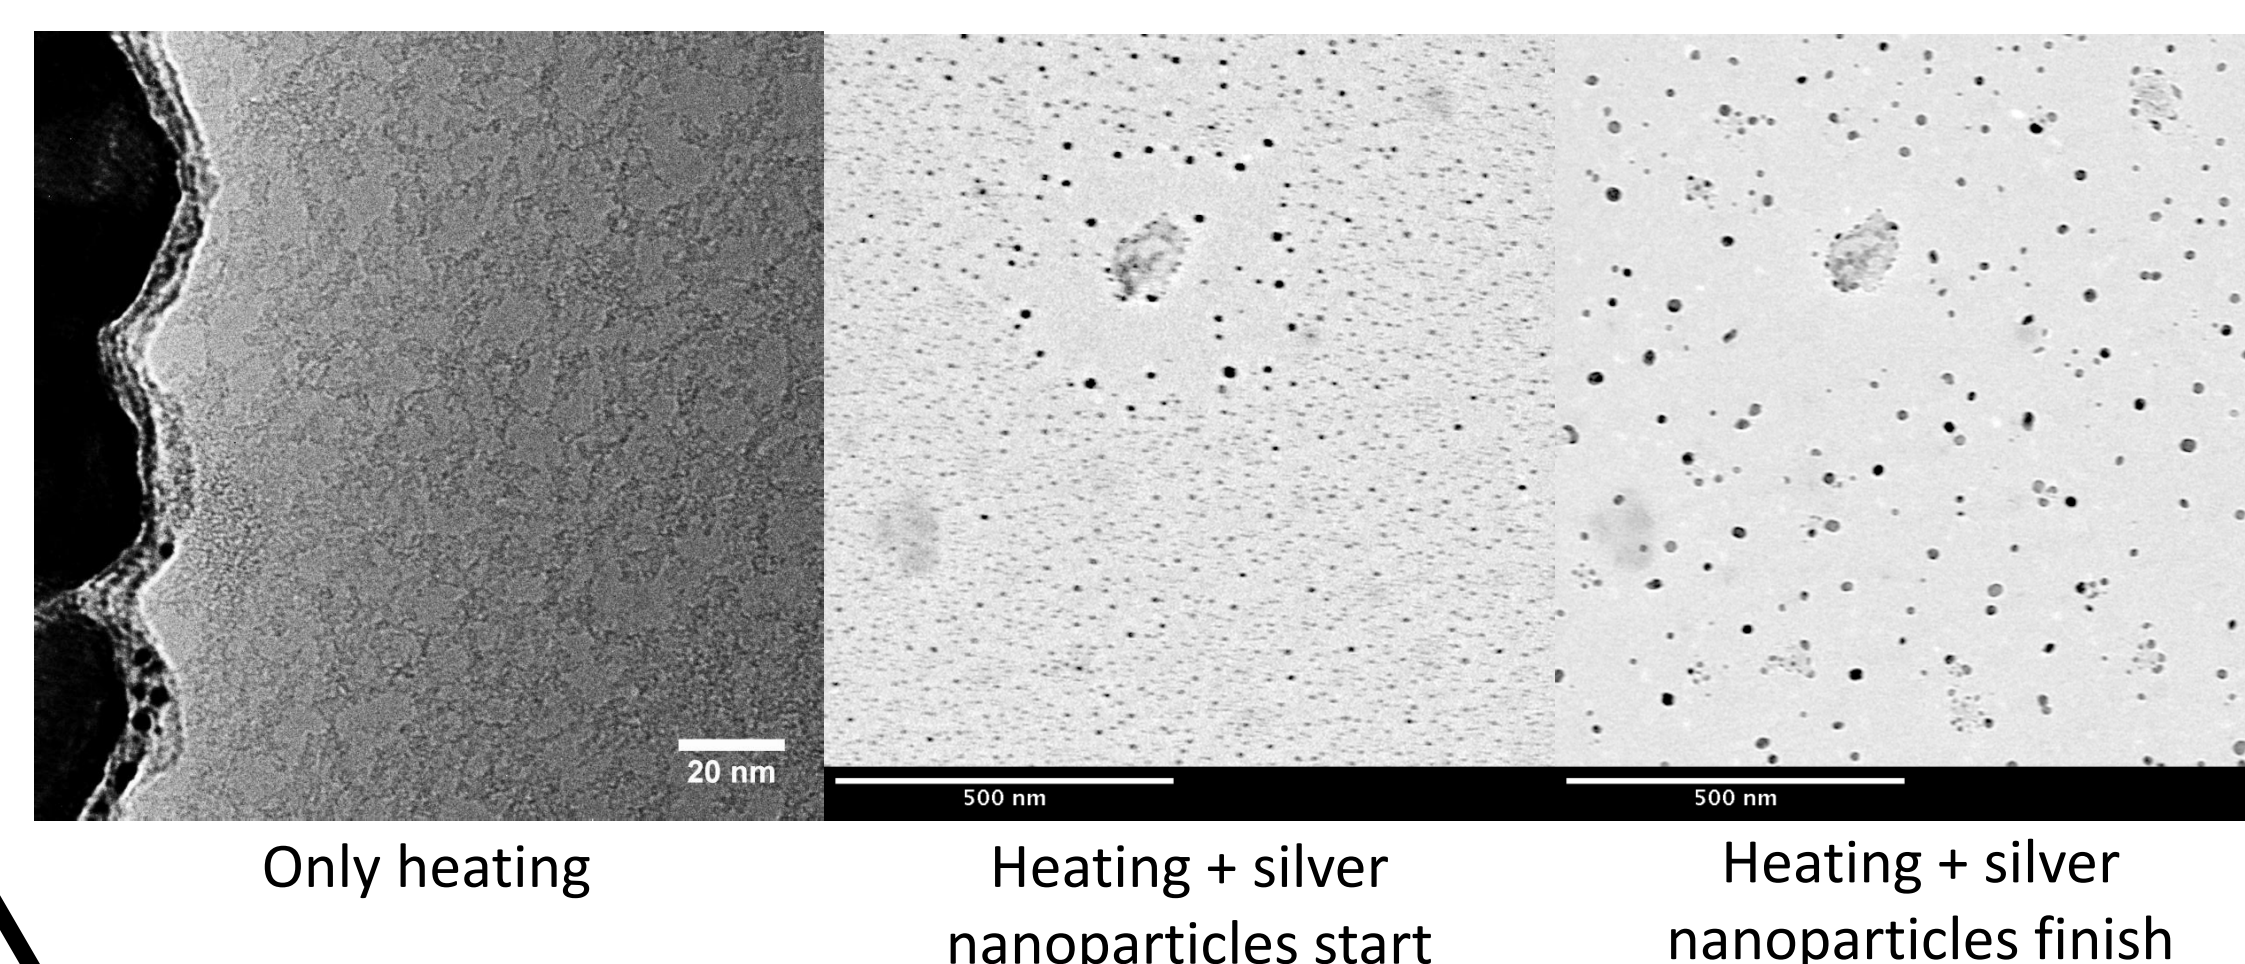

The work leading to these results has received funding from the European Union Seventh Framework Programme (FP7/2007-2013) under grant agreement n $^{\circ}$ FP7-604000

